

Lithium-Ion Battery Materials and Mechanical Stress Fields

Yixu Richard Wang¹ and Hsiao-Ying Shadow Huang^{2,✉}

Abstract: Lithium-ion batteries have been used for a wide range of applications, from power tools and portable electronics to recent plug-in hybrid electric vehicles and pure electric vehicles. However, current prototype Li-ion batteries have been reported to lose capacity or degrade rapidly under high discharging rate. In this work, we provided an overview of commercially available cathode materials for Li-ion rechargeable batteries and focused on characteristics that give rise to optimal energy storage systems for future transportations. In this study, we hypothesized that the mechanical and structural failures were attributed to dislocations formations. Numerical models and crystal visualizations were provided to further understand the stress development due to lithium movements during charging or discharging. This work will contribute to the fundamental understanding of the mechanisms of capacity loss in lithium-ion battery materials and thus leads to economic and environmental benefits.

Keywords: Li-ion batteries, Cathode, Dislocations, Stress Analysis.

1. INTRODUCTION

A. The Need for Rechargeable Batteries

For over a century, petroleum-derived fuels have been the first choice as an energy source for transportation, and accounted for more than 71.4% of U.S. petroleum use in 2009 [1]. Although the petroleum-based fuel energy resource is convenient and technically matures, researchers started looking for alternative energy sources such as batteries due to the shortage of petroleum and because burning fossil fuels have become an environmental issue. It is reported that 98% of carbon dioxide emissions come from petroleum fuels [2]. Since carbon dioxide accounts for the largest share of greenhouse gases, to meet the stated goal of reducing total U.S. greenhouse gas emissions to 83% below 2005 levels by 2050, an alternative energy storage system is required.

One of the most promising energy storage solutions for future automotive technology is the rechargeable battery. Compared with other resources such as flywheels, capacitors, biofuel, solar cells, and fuel cells, rechargeable batteries are more portable and provide quick energy storage and release [3-5]. Moreover, it is more difficult to use these other resources globally than it is to use rechargeable batteries, due to the operating environment limitations for these other energy sources [3]. Compared with capacitors,

rechargeable batteries have lower self-discharge rates [3, 5], thus holding their charge for longer periods of time. Therefore, to best serve as a future automotive technology, rechargeable batteries should have high energy and power densities [4], the ability to output high current for a long period of time, and to be fully charged quickly. The durability and environmental friendliness of rechargeable batteries is also very important. They should work for several years safely under different climatic conditions, and even if involved in an unfortunate car collision.

B. Fundamental Science in Li-ion Battery Materials

Among the rechargeable batteries, Li-ion batteries have dominated the field of advanced power sources due to their high gravimetric and volumetric energy density [6]. The most common Li-ion battery applications in the market are for portable electronics, power tools, and transportation. Li-ion battery contains three main parts: cathode, anode, and the electrolyte. It operates via an electrochemical process in which lithium ions are shuttled between cathode and anode while electrons flow through an external wire to form an electrical circuit. During discharge, an electrical circuit is formed, and lithium ions move out (extraction) from the anode to the cathode (intercalation) to neutralize these charges. The reactions occur continuously and while electrons continue to flow, providing electrical energy to the connected device. The electrical energy is then restored to the battery upon recharge. Both anode and cathode materials exhibit layered structures, which allow lithium ions to stay in or pass through the structures. In the cathode side, intercalated lithium compound such as LiFePO_4 , LiMn_2O_4 , and LiCoO_2 are commonly used. In the anode side, layered carbon materials (graphite or carbon nanotube) [7-8], titanate materials [9], or silicon nanowires [10] are widely used due to their low electrochemical potential with respect to Li metal [11]. The most common electrolyte is a solution that contains lithium salt in an organic solvent. To avoid unnecessary reactions between electrode materials and H/H_2 or $\text{O}_2/\text{H}_2\text{O}$ in electrolyte, organic solvent or organic solid are adopted to replace aqueous solvent [11]. The current collectors, connecting to anode and cathode, carry electrons and transit the current to the external circuit. The separator is a membrane that lies between anode and cathode to avoid a possibility of short circuit.

C. The Prospective Cathode Materials

In this study, we provide an overall comparison of commonly used cathode materials for Li-ion batteries. There are four mainstream cathode materials in the present market: LiCoO_2 , LiMn_2O_4 , LiNiO_2 , and LiFePO_4 . LiCoO_2 is the most commonly used in portable electronic devices due

¹Yixu Richard Wang, Mechanical and Aerospace Engineering Department, North Carolina State University (ywang30@ncsu.edu)

²Hsiao-Ying Shadow Huang (✉) Mechanical and Aerospace Engineering Department, North Carolina State University (hshuang@ncsu.edu)

to its excellent charging/discharging rate and power/energy density [12]. However, a battery with LiCoO₂ as its cathode material does not have good thermal stability [13]. Moreover, Co is toxic and expensive, which makes LiCoO₂ an imperfect choice for a cathode material for electric vehicles (EVs), hybrid electric vehicles (HEVs), and plug-in hybrid electric vehicles (PHEVs). LiMn₂O₄ is able to provide higher voltage, but it does not have a good power/energy density [14]. Its relatively short cycle life and high capacity loss [15] indicate that it is not an ideal cathode material for Li-ion batteries for EV/HEV/PHEV applications. The LiNiO₂ material, with the same structure as LiCoO₂, provides good power and energy densities [16]. However, since it is very difficult to prepare pure LiNiO₂ composite, Co-doped LiNiO₂, Li_{1-x}(Ni_{0.8}Co_{0.2})_{1+x}O, is usually considered as an alternative material in research and applications [17]. With the demand for Li-ion batteries increasing worldwide, a new Li-ion battery cathode material, LiFePO₄, was developed by Goodenough in 1996 [18]. He and his group discovered that LiFePO₄ is a good candidate for a cathode material due to its low price and high thermal stability. However, LiFePO₄ suffers from low intrinsic electronic conductivity (10⁻¹⁰–10⁻⁹ Scm⁻¹) [19]. Based on the study by Chung and Chiang [20], the low electronic conductivity of LiFePO₄ could be significantly enhanced by doping other metal elements such as zirconium, niobium, and magnesium [20]. In the following section, characteristics and specifications of aforementioned cathode materials were collected and compared for Li-ion batteries. Specifically, we focus on (1) volumetric power and energy densities, (2) gravimetric power and energy densities, (3) stability, safety and environmental factors, and (4) capacity and rate-capacity.

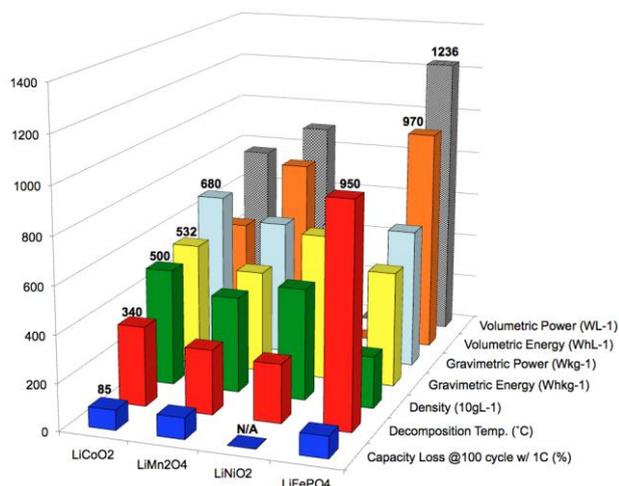


Fig. 1: Comparison of various cathode materials, LiCoO₂, LiMn₂O₄, LiNiO₂, and LiFePO₄, looking at the volumetric power/energy, gravimetric power/energy, density, decomposition temperature, and capacity loss. The capacity is measured as the hourly (dis)charge rate for 100 cycles. Among these materials, LiFePO₄ provides high volumetric power/energy, gravimetric energy, low density, high decomposition temperature, and comparable capacity loss. This suggests that LiFePO₄ is the choice for compact and lightweight energy materials.

D. Characteristics of Cathode Materials

1) *Volumetric Power and Energy Densities*: Power and energy densities are important properties for cathode materials. They determine the energy release rate and energy storage capacity per unit weight or volume. For electric vehicles, the volumetric power density and energy density are very important, because with the same energy capacity, a smaller battery is easier to fit into a car. For battery cathode materials: it is observed that LiFePO₄ has the highest volumetric power density and energy density (1236 WL⁻¹, 970 WhL⁻¹, respectively) among the four mainstream cathode materials [21-22] (Fig. 1). LiCoO₂ has a volumetric power density of around 767 WL⁻¹ and an energy density of around 483 Wh/L. These values are roughly half that of LiFePO₄ [21-22] (Fig. 1). LiMn₂O₄ has a volumetric power density and energy density (900 WL⁻¹, 785 WhL⁻¹) higher than those of LiCoO₂. However, LiMn₂O₄ has a slightly lower volumetric power density and energy density than that of LiFePO₄ [21-22] (Fig. 1). The volumetric power and energy density data of LiNiO₂ were not available since pure LiNiO₂ is difficult to prepare. In addition, the United States Advanced Battery Consortium (USABC) listed goals for advanced batteries for EVs where volumetric power density should at least be 600 WL⁻¹ and the volumetric energy density should at least be 300 WhL⁻¹ [23] (Table 1). Considering batteries as a whole (including cathode, anode, and electrolyte), current battery technologies, however, are only able to deliver 250-360 WhL⁻¹ for LiCoO₂ batteries, 330 WhL⁻¹ for LiMn₂O₄ batteries, 450 WhL⁻¹ for LiNiO₂ batteries, and 220 WhL⁻¹ for LiFePO₄ batteries. Therefore, the performance of advanced batteries still falls short of the EV goals set forth in 2006 by USABC [23]. Note that the values reported in Figure 1 are based on raw materials and the values reported in Table 1 are batteries as a whole (including cathode, anode, and electrolyte) with the said cathode materials.

2) *Gravimetric Power and Energy Densities*: The gravimetric power and energy densities are very important for portable devices. That is, with the same power and energy capacity, a lighter battery is easier to carry [22, 24-25]. It is observed that LiNiO₂ has high gravimetric power and energy densities of 600 Wkg⁻¹ and 629 Whkg⁻¹, respectively (Fig. 1). The gravimetric power density of LiFePO₄ is reported around 600 Wkg⁻¹ whereas its gravimetric energy density (495 Whkg⁻¹) is lower than that of LiNiO₂. LiCoO₂ has a gravimetric power density of around 680 Wkg⁻¹ and an energy density of around 532 Whkg⁻¹. These values are slightly higher than that of LiFePO₄ [22, 24-25] (Fig. 1). Finally, LiMn₂O₄ has a gravimetric power density of around 584 Wkg⁻¹ and an energy density of around 440 Whkg⁻¹. These values are comparable to that of LiFePO₄ [22, 24-25] (Fig. 1). The density of each cathode material was also listed in Fig. 2. LiFePO₄ has the lowest density (2.2 kgL⁻¹) and LiCoO₂ has the highest (5 kgL⁻¹), which is more than twice of that of LiFePO₄. Gravimetric power/energy densities should not be directly converted to volumetric power/energy densities based on the provided density values. This is due to the different synthetic methods that were chosen based on

different demands, and the weight of electrolytes was sometimes included in the collected data when the gravimetric power and energy densities were calculated. According to the USABC, gravimetric power density should at least be 400 Whkg^{-1} and the gravimetric energy density should at least be 200 Whkg^{-1} [23] (Table 1). However, considering batteries as a whole (including cathode, anode, and electrolyte), current battery technologies are only able to deliver $106\text{-}250 \text{ Whkg}^{-1}$ for LiCoO_2 batteries, 100 Whkg^{-1} for LiMn_2O_4 batteries, 192 Whkg^{-1} for LiNiO_2 batteries, and $90\text{-}110 \text{ Whkg}^{-1}$ for LiFePO_4 batteries. Therefore, the performance of advanced batteries falls short of EV goals set forth in 2006 by the USABC [23].

TABLE 1.

VOLUMETRIC AND GRAVIMETRIC ENERGY DENSITY FOR 4 DIFFERENT TYPES OF LI-ION BATTERIES AND THE COMPARISON TO USABC REQUIREMENTS.

Energy Density	LiCoO_2	LiMn_2O_4	LiNiO_2	LiFePO_4	USABC
Volumetric (WhL^{-1})	305	330	450	220	300
Gravimetric (Whkg^{-1})	180	100	170	130	200

3) *Stability, Safety, and Environmental Factors:* The safety issue for Li-ion batteries is an important factor that determines potential applications, especially for EV/HEV/PHEV and other electronic devices. Battery safety is attributed primarily to the material's thermal stability, and the reported overheating and explosion of Li-ion batteries is mainly due to a battery's thermal instability [26]. The differential scanning calorimetry (DSC) test is widely used to investigate the exothermic or endothermic reaction for composite explosives. It determines the ability of a material to absorb or release heat during electrochemical reactions such as lithium insertion or extraction in Li-ion batteries. By using DSC testing, Xia et al. [27] collected the thermal activity and predicted the resultant thermal stability for different cathode materials. They observed that LiFePO_4 has the lowest exothermic peak temperature (289°C) and exhibited endothermic heat flow (-6 Wg^{-1}). That is, during electrochemical reactions, LiFePO_4 will see smaller temperature increases than with the other three cathode materials. Moreover, it is observed that LiMn_2O_4 has an exothermic peak at 302°C , which can easily be reached during a car accident. LiCoO_2 and LiNiO_2 also release heat and cause overheating or even explosion at higher temperatures of around $300\text{-}400^\circ\text{C}$, suggesting that LiCoO_2 and LiNiO_2 as cathode materials are an undesirable choice for energy storage systems for EV/HEV/PHEV applications. In contrast, the electrochemical reaction of LiFePO_4 is endothermic, suggesting that LiFePO_4 is a safer battery material. In general, exothermic peak temperature can be used as a description of self-reaction temperature. The lower the peak temperature, the safer a material is. The decomposition temperature also indicates that LiFePO_4 (950°C) has much higher thermal stability than any other material (Fig. 1). The decomposition temperatures for

LiCoO_2 , LiMn_2O_4 , and LiNiO_2 are 340°C , 275°C , and 250°C , respectively (Fig. 1) [27].

In addition to the safety issue, we also compare the cost of cathode materials and environmentally-related factors (Table 2). We note that Co is toxic and Ni has the potential to cause heavy metal pollution. LiFePO_4 is made from non-toxic materials and the transition metal is abundant (160 billion tons in the Earth). As a result, batteries made from this type of cathode material could be relatively cheaper than that of LiCoO_2 since the transition metal storage of LiCoO_2 is approximately 8.3 million tons (0.005% of LiFePO_4). The transition metal storage of LiMn_2O_4 and LiNiO_2 are 99.7 million and 48 billion tons, respectively. It is suggested that LiFePO_4 as a cathode material for rechargeable batteries is more environmental friendly and cost effective than the other three cathode materials (Table 2).

TABLE 2.

THERMAL STABILITY CHARACTERISTICS AND OTHER FACTORS IN COST AND ENVIRONMENTAL ISSUES FOR BATTERY MATERIALS.

	LiCoO_2	LiMn_2O_4	LiNiO_2	LiFePO_4
Exothermic peak temperature ($^\circ\text{C}$)	367	302	348	289
Exothermic heat flow (Wg^{-1})	20	7	33	-6
Environmental pollution	toxic Co	good	heavy metal Ni	good
Battery cost	expensive	moderate	cheap	cheap
Storage of transition metal ($\times 10^6$ ton)	8.3	99.7	48,000	160,000

4) *Capacity and Rate-capacity:* The capacity of a battery is the amount of charge available expressed in milliampere-hours (mAh), and it depends on discharge conditions such as the magnitude of the current, the voltage of the battery, temperature, and other factors. Rate-capacity loss after thousands cycling is one of the biggest obstacles for advanced rechargeable battery technology. To better examine the rate-capacity, four mainstream cathode materials were compared for their retained capacity. The retained capacity of cathode materials is measured after a certain amount of cycles at an nC discharge rate, where a rate nC corresponds to a full discharge in $1/n$ hours. For example, 0.25C is the rate in which a battery is totally discharged in 4 hours. The higher the value of the rate nC, the better the energy output ability of the battery material is. Studies showed that after 100 cycles at 1C-rate discharging, LiFePO_4 processes 92% capacity retention, LiMn_2O_4 processes 90% and LiCoO_2 processes 85% capacity retention, respectively [28] (Fig. 1). By extrapolation, if the capacity retention is measured under a higher rate ($n > 1$), LiFePO_4 has a better capability to maintain rate-capacity than that of other cathode materials. Since the preparation and synthetic methods for LiNiO_2 are extremely difficult, its capacity retention data is unavailable. Nevertheless, the rate-capacity loss of LiFePO_4 is reported after thousand-cycles high-rate discharging [29-30]. It is observed that under a high discharge rate, the capacity retention rate of LiFePO_4 batteries is not as good as that of other batteries.

2. FACTORS OF ELECTRODE FAILURE

Electrode failures of Li-ion batteries are usually a result of the accumulation of aging or degradation, which affect electrodes' ability to hold charge and result in capacity loss of Li-ion batteries, and the mechanism could be categorized based on storage/cycling or chemical/mechanical activities. For anode materials, the aging/degradation mechanism is primarily determined by the development of solid-electrolyte interphase (SEI) film [31], it is a chemical reaction. For cathode materials, the aging/degradation mechanisms could be categorized into 2 groups: (1) ones would cause the loss of active material via storage and cycling, such as chemical interaction of aging products with anodes, oxidation of electrolyte components, and surface film formation [29-35], (2) ones would increase the battery impedance or decrease the output voltage, such as structural changes, electrode components changes, or materials degradation [36-38] (Fig. 2). In general, the aforementioned four phenomena do not happen alone and mechanism of electrode failure is caused by several factors taking place at the same time, which makes it more complicated.

Cathode materials are considered as the vital part of Li-ion batteries since cathode materials affect both performance and cycling life of Li-ion batteries. Since aging/degradation mechanism of cathode materials is much more complicated than that of anode materials, and since there are varieties of electrode materials, it is difficult to provide a general explanation for cathode aging/degradation mechanisms in all Li-ion systems. In this article, the authors focus on basic factors such as storage, state of charge, and Jahn-Teller effect.

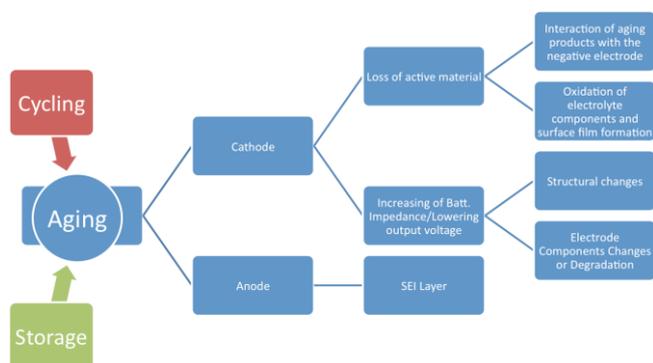


Fig 2. Electrode aging/degradation categories based on different causes and influences. The proposed work focuses on understanding the interplay between structural changes and deterioration in LiFePO₄ cathode material.

While storing electrode materials, aging/degradation usually occurs because of the side reactions due to thermodynamic instability of materials [39-42]. Moreover, the state of charge, cycling conditions, and temperature are three main factors that cause materials age/degrade. Finally, cycling with kinetically induced effects, such as volume variations and concentration gradients, could potentially result in the capacity loss of Li-ion batteries.

A. Storage

As the cathode material of Li-ion batteries, LiFePO₄ is the promising green material at present for its low cost, non-toxicity, rich source of raw materials and great electrochemical performance [43]. Yet, although commonly considered as highly stable toward air and H₂O, aging/degradation of the electrochemical performance of LiFePO₄ was shown after being exposed to air for a few weeks at ambient temperature [44]. To observe the side reaction and side phase of LiFePO₄ materials in the atmosphere of humid-hot air, a nano-scaled sample of LiFePO₄ material (70 nm) in 120°C hot air was stored for 30 days. By comparing it with a pristine sample under the X-ray Diffraction (XRD) test, the decreasing unit-cell volume after storing in high temperature was observed, suggesting that the delithiation occurred during hot-air [45]. In the parallel study to the XRD test, the decreased unit-cell volume is calculated based on Vegard's Law, which equivalents to 11% lithium missing during the high temperature storage. Moreover, the amount of Fe³⁺ determined by the Mossbauer spectroscopy accounts for 45% of total iron, which is far more than 11% loss of lithium. This phenomenon indicates that while storing, in addition to the trivalent Fe from delithiation, an amorphous ferric phosphate side-phase grows detrimentally to olivine LiFePO₄ upon air exposure. Therefore, this loss of active materials in LiFePO₄ cathode materials could potentially lead to the capacity loss for Li-ion batteries.

B. State of Charge

In current EV/HEV/PHEV markets, LiMn₂O₄ is adopted as cathode materials for Li-ion batteries [46]. LiMn₂O₄ cathode materials provide higher voltage than other materials, but its usage is limited by its short cycle life [15, 47-48]. It is observed that the accelerated aging/degradation of LiMn₂O₄ cathode materials is due to the dissolution of Mn in electrolyte under various charging voltage: with a higher charging voltage than 4.2V or nearly fully discharged. During very low state of charge or a high temperature (55°C), a disproportionation reaction will occur, which consumes two Mn³⁺ at two Mn sites in LiMn₂O₄ cathode materials while Mn³⁺ is converting to Mn²⁺ and Mn⁴⁺ [15, 31, 48]. The Mn⁴⁺ stays in one of the two Mn sites and takes the place of Mn³⁺. Mn²⁺ ions, on the other hand, escape from LiMn₂O₄ and dissolve in the electrolyte. The empty Mn site caused by the Mn²⁺ dissolution is then replaced by a lithium ion. Therefore, new composite materials Li[LixMn_{2-x}]O₄ is produced. Due to the element change on Mn sites in spinel structure, structural change happens during the dissolution. Moreover, the LiPF₆, which solute in electrolyte as conductive salt, turns to HF acid at times. HF acid could then react with Li[LixMn_{2-x}]O₄ material and make it soluble in electrolyte. After Mn²⁺ ions getting into the electrolyte, many side reactions could be activated [49-51].

C. Structure and Jahn-Teller Effects

Structure failure of cathode materials caused by phase transformations during the insertion and desorption of lithium

ion is a main factor that influences the aging/degradation mechanisms. A perfect eight-unit cell crystal LiFePO_4 model without dislocations is shown in Fig. 3(a) and lithium ions lay in the spaces along the b(y)-direction in the crystal. The crystal structure is made up by FeO_6 octahedras, PO_4 tetrahedras and lithium ions (Fig. 3b). During discharging and charging, lithium ions shuttle in and out of the crystal through the spaces along the b(y)-axis and potentially lead to structural distortions or failures.

The olivine-type crystal structure of LiFePO_4 belongs to space group Pnma, in which Li, Fe and P atoms occupy octahedral 4a (0, 0, 0), octahedral 4c (x, $\frac{1}{4}$, z) and tetrahedral 4c (x,y,z) sites, respectively (Fig. 4-a). A FeO_6 octahedra lies in the middle and is surrounded by five PO_4 tetrahedras (Fig. 4-b). One of the PO_4 tetrahedras shares an edge (O-O bond) with the FeO_6 octahedra, and the other four share four corners respectively. The structures of LiFePO_4 and FePO_4 have similar crystal structures except for the lattice parameter of FePO_4 is smaller than that of LiFePO_4 , due to differences in lattice parameters of LiFePO_4 ($a=10.334\text{\AA}$, $b=6.002\text{\AA}$, $c=4.695\text{\AA}$) and FePO_4 ($a=9.826\text{\AA}$, $b=5.794\text{\AA}$, $c=4.784\text{\AA}$); mismatch occurs during the phase transformation. The differences in lattice parameters could also be attributed to the different valences of Fe: the valence of Fe is +2 for LiFePO_4 , and the valence of Fe is +3 for FePO_4 [52-53]. The difference in lattice parameter could be related to the Jahn-Teller effect. It states the relationship between metal valences and lattice parameters, which could be used to justify lattice parameter changes of LiFePO_4 and FePO_4 [54-61]. In short, the outer shell electrons of an atom have strong shielding effect causing by charge neutralization between outer shell electrons and atomic nucleus. The shielding effect would cancel out parts of the electrostatic forces between the atomic nucleus and atoms around it. Changing the valence of an atom will lead to different electron configuration and that in outer shell will have different intensity of shielding effect in each direction. Therefore, when Li-ions move out from LiFePO_4 , the valence of Fe-ions changes, and then the shielding effect in different directions around Fe-ions change; this phenomenon may cause the structure of Fe octahedra to change.

3. MECHANICAL STRESS FIELDS IN BATTERY MATERIALS

In this article, previous works on dislocation based stress field are discussed and stress distributions in LiFePO_4 cathode materials are provided. We choose LiFePO_4 as our model system due to: (i) It is recognized that LiFePO_4 is a promising cathode material for Li-ion batteries, thus understanding stress accumulations inside the material is important for developing longer-lasting Li-ion battery materials. (ii) LiFePO_4 has a 3D matrix structure with anisotropic elastic materials property. Once we successfully build up a model system for this sophisticated material, we are then able to provide a general mathematical framework for other Li-battery cathode materials, such as LiCoO_2 ,

LiMnO_2 , and LiNiO_2 .

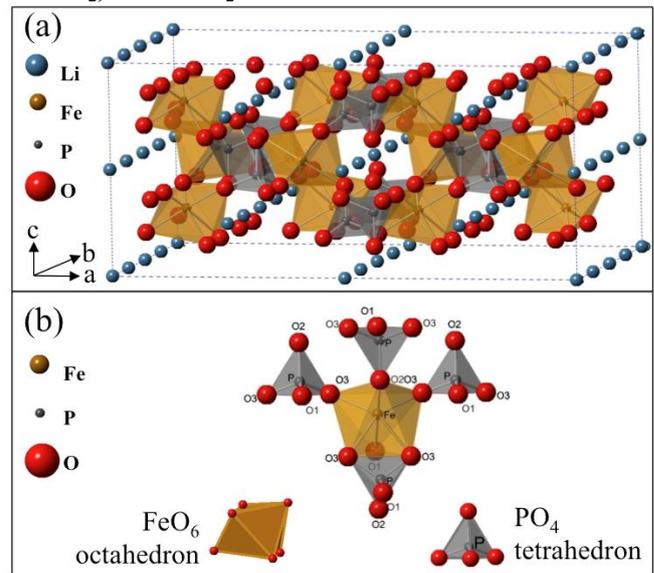


Fig. 3. (a) Eight LiFePO_4 unit cells without dislocations where lithium ions lay in the spaces along the b(y)-direction. (b) A FeO_6 octahedras and five PO_4 tetrahedras connect each other by sharing one edge and three corners.

Chen et al. observed cracks in LiFePO_4 particles from SEM images, suggesting accumulation of dislocations [62], the cracks along c(z)-direction was also observed. With $\text{Li}_{0.5}\text{FePO}_4$ samples, a slight rotation around b(y)-direction of the two phases was observed, indicating the deformation and dislocation associated with delithiation. Therefore, the distortion zones and dislocations could potentially form via phase transformations during the insertion and desorption of lithium ions and potentially leads to structural failures [63-64]. Moreover, it is observed that the lithium ion insertion and extraction process leads ~7% volume change between LiFePO_4 and FePO_4 phase crystals. It is due to internal stress and strain accommodations occur in LiFePO_4 crystals because of the coherent interface between phase boundaries [65]. The internal strains initiate dislocations that form after several intercalation-extraction cycles inside cathode materials, and these dislocations potentially lead the growth of minor cracks.

In 1953, J. D. Eshelby et al. developed general solutions for evaluating dislocation stresses for an arbitrary homogeneous anisotropic solid material [66]. Elastic equations for pure screw dislocation lines with infinite length in monoclinic crystal system materials and for pure edge dislocation lines with infinite length in orthorhombic crystals were developed. However, limited by computational methods at that time, only few equations for simple cases were fully solved. With the developments of computers, stress distribution around dislocations with anisotropic materials properties were illustrated [67]. Recently, solutions for stress fields of dislocation loops have been developed [68]. In 1975, H. L. Heinisch et al. calculated the elastic stress field, self-energies, and energy factors of straight edge and screw dislocations in olivine materials [67]; stress distributions were provided for different

directions of dislocations. From their results, Heinisch *et al.* concluded that orthorhombic olivine materials have moderate elastic anisotropy, though the effects of anisotropy seem to be relatively small. According to their model, they did not successfully predict the slip directions and glide plane preference of dislocations for orthorhombic anisotropic materials based on the elasticity theory.

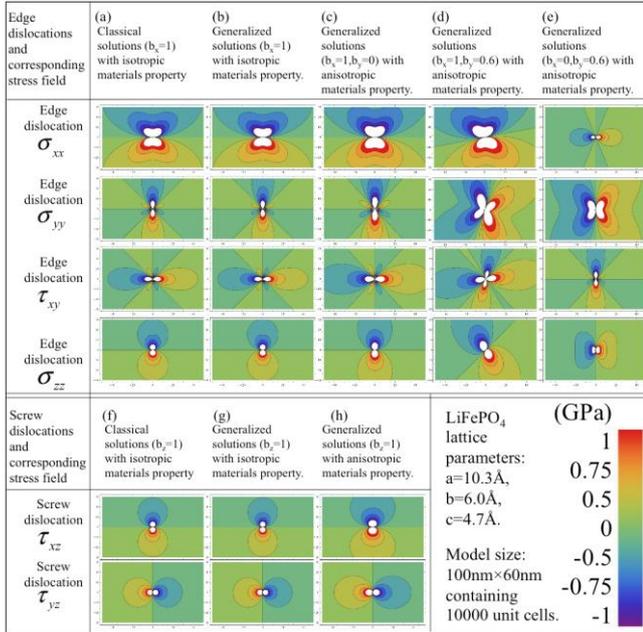


Fig. 4. The stress field for edge and screw dislocations. (a) Stress distribution calculated via classical solutions for a single edge dislocation with isotropic materials property. (b) & (c) Stress distribution calculated via generalized solutions for a single edge dislocation with isotropic and anisotropic materials property, respectively. (d) & (e) Stress distribution for varied Burger's vector directions where generalized solutions for a single edge dislocation with anisotropic materials property are adapted. (f) Stress distribution calculated via classical solutions for a single screw dislocation with isotropic materials property. (g) & (h) Stress distribution calculated via generalized solutions for a single screw dislocation with isotropic and anisotropic material properties, respectively.

In this article, we provide dislocation stress distributions for LiFePO_4 crystals (Fig. 4). Based on the lattice parameters of LiFePO_4 , we set the dimension as $100L \times 100L$ on the $a(x)$ - $b(y)$ plane, where $L=10\text{\AA}$. It is a plausible model size due to: (i) the reported LiFePO_4 particle size is among several hundred nanometers^[69], which could be correctly represented by $100L \times 60L$ in our model system, (ii) our model size of $100L \times 60L$ is sufficient to avoid $4L \times 4L$ dislocation core regions, the region within which the elastic solutions would not be valid^[70], and (iii) our model size of $100L \times 60L$ is sufficient to depict overall stress distributions without any boundary effects. Classical^[70] and generalized^[71] stress field for a single edge dislocation (with Burger's Vector, $b_x=1$ and $b_y=0.6$) with isotropic materials property^[72] were compared in Figure 4(a) and (b). Similarly, classical and generalized stress field for a screw dislocation (with Burger's Vector, $b_z=0.47$) with isotropic materials property^[72] were compared in Figure 4(f) and (g). The results suggest generalized stress field are equivalent to

classical ones, which provide us a solid basis to vary materials properties on the said generalized solutions. By incorporating anisotropic material property of LiFePO_4 ^[72] into our model systems, the results reveal that the stress fields are comparable to ones with isotropic materials property (Fig. 4(c) and (h)), which is in the agreement of Heinisch *et al.*: the effects of anisotropy for orthorhombic olivine materials is insignificant^[67].

In most cases, Burger's vectors are not perfectly parallel to one specific axis. Therefore, we expand our model system to exam stress variations for arbitrary Burger's vector's directions. Interesting stress fields are observed for $b_x=1$, $b_y=0.6$ in Fig. 4(d) and $b_x=0$, $b_y=0.6$ in Fig. 4(e). Comparing with stress field in Fig. 4(a) and the one in Fig. 4(e), it is suggested that stress values for arbitrary Burger's vector's directions could be simply calculated by utilizing linear transformations. Moreover, the stress field for the screw dislocation is derived via the displacement in the $c(z)$ -direction, therefore Burger's Vectors in x and y directions are unavailable.

4. CONCLUSION

This study provides an overview of four mainstream lithium-ion battery cathode materials. Characteristics of LiCoO_2 , LiMn_2O_4 , LiNiO_2 , and LiFePO_4 were collected and compared. Specifically, we focused on specifications for (1) volumetric power and energy densities, (2) gravimetric power and energy densities, (3) stability, safety and environmental factors, and (4) capacity and rate-capacity. Since synthetic methods are different for the four different cathode materials, only the representative data that appeared most frequently within the past five years were chosen to ensure that data from different literature sources are comparable. Current electrochemical technology is still limited to developing cathode materials to achieve EV goals set by the USABC. The main obstacle for advanced rechargeable batteries is found in the rate-capacity loss at high C-rate discharging. It is currently one of the most challenging issues in developing energy storage systems for EV/HEV/PHEV, and the enhancement of rate-capacity retention is the primary design goal of battery chemistry in the electrochemical community.

Moreover, we report stress fields caused by a single dislocation inside LiFePO_4 particles. Different dislocations with different Burgers vectors directions have significant influences in the stress developments. With multiple dislocations accumulations and interactions^[73], fractures of LiFePO_4 are formed and observed experimentally. It is believed that fractures inside LiFePO_4 are potential failure mechanisms responsible for the rate-capacity loss in Li-ion batteries. This study contributes to the fundamental understanding of the stress development in cathode materials and it is related to the capacity loss in lithium-ion battery. This study helps the design of better rechargeable batteries, and thus advances technology in energy storage systems for future transportation.

REFERENCES

- [1] U.S. Department of Energy, 2010, "Monthly Energy Review," U.S. Energy Administration, DOE/EIA-0035(2010/12), Office of Energy Statistics, U.S. Department of Energy, Washington, DC 20585.
- [2] U.S. Department of Energy, 2009, "Emissions of Greenhouse Gases in the United States, 2008," U.S. Energy Administration, DOE/EIA-0573(2008), Office of Energy Statistics, U.S. Department of Energy, Washington, DC 20585.
- [3] Ibrahim, H., Ilinca, A., and Perron, J., 2008, "Energy Storage systems—Characteristics and Comparisons," *Renewable and Sustainable Energy Reviews*, 12(5) pp. 1221-1250.
- [4] Cutler J. Cleveland, 2004, "Encyclopedia of Energy," Elsevier, New York, .
- [5] Kurzweil, P., 2009, "Encyclopedia of Electrochemical Power Sources," Elsevier, Amsterdam, pp. 607-633.
- [6] Gao, X. P., and Yang, H. X., 2010, "Multi-Electron Reaction Materials for High Energy Density Batteries," *Energy & Environmental Science*, 3(2) pp. 174-189.
- [7] Chang, H., Wu, H., and Wu, N., 2008, "Enhanced High-Temperature Cycle Performance of LiFePO₄/carbon Batteries by an Ion-Sieving Metal Coating on Negative Electrode," *Electrochemistry Communications*, 10(12) pp. 1823-1826.
- [8] Masarapu, C., Subramanian, V., Zhu, H., 2009, "Long-Cycle Electrochemical Behavior of Multiwall Carbon Nanotubes Synthesized on Stainless Steel in Li Ion Batteries," *Advanced Functional Materials*, 19(7) pp. 1008-1014.
- [9] Liu, P., Sherman, E., and Verbrugge, M., 2010, "Electrochemical and Structural Characterization of Lithium Titanate Electrodes," *Journal of Solid State Electrochemistry*, 14(4) pp. 585-591.
- [10] Chan, C. K., Peng, H., Liu, G., 2008, "High-Performance Lithium Battery Anodes using Silicon Nanowires," *Nature Nanotechnology*, 3(1) pp. 31-35.
- [11] Goodenough, J. B., and Kim, Y., 2010, "Challenges for Rechargeable Li Batteries," *Chemistry of Materials*, 22(3) pp. 587-603.
- [12] Takahashi, Y., Tode, S., Kinoshita, A., 2008, "Development of Lithium-Ion Batteries with a LiCoO₂ Cathode Toward High Capacity by Elevating Charging Potential," *Journal of the Electrochemical Society*, 155(7) pp. 537-541.
- [13] Choi, K., Jeon, J., Park, H., 2010, "Electrochemical Performance and Thermal Stability of LiCoO₂ Cathodes Surface-Modified with a Sputtered Thin Film of Lithium Phosphorus Oxynitride," *Journal of Power Sources*, 195(24) pp. 8317-8321.
- [14] Huang, Y., Li, J., and Jia, D., 2004, "Preparation and Characterization of LiMn₂O₄ Nanorod by Low Heating Solid State Coordination Method," *Journal of Nanoparticle Research*, 6(5) pp. 533-538.
- [15] Liu, H., and Tang, D., 2009, "The Effect of Nanolayer AlF₃ Coating on LiMn₂O₄ Cycle Life in High Temperature for Lithium Secondary Batteries," *Russian Journal of Electrochemistry*, 45(7) pp. 762-764.
- [16] Han, C., Kim, J., Paeng, S., 2009, "Electrochemical Characteristics of LiNiO₂ Films Prepared for Charge Storable Electrode Application," *Thin Solid Films*, 517(14) pp. 4215-4217.
- [17] Fu, X., Wang, X., Peng, H., 2010, "Low Temperature Synthesis of LiNiO₂@LiCoO₂ as Cathode Materials for Lithium Ion Batteries," *Journal of Solid State Electrochemistry*, 14(6) pp. 1117-1124.
- [18] Padhi, A. K., Nanjundaswamy, K. S., and Goodenough, J. B., 1997, "Phospho-Olivines as Positive-Electrode Materials for Rechargeable Lithium Batteries," *Journal of the Electrochemical Society*, 144(4) pp. 1188-1194.
- [19] Awarke, A., Lauer, S., Pischinger, S., 2011, "Percolation-Tunneling Modeling for the Study of the Electric Conductivity in LiFePO₄ Based Li-Ion Battery Cathodes," *Journal of Power Sources*, 196(1) pp. 405-411.
- [20] Chung, S., Bloking, J. T., and Chiang, Y., 2002, "Electronically Conductive Phospho-Olivines as Lithium Storage Electrodes," 1(2) pp. 128.
- [21] Cheon, S. E., Kwon, C. W., Kim, D. B., 2000, "Effect of Binary Conductive Agents in LiCoO₂ Cathode on Performances of Lithium Ion Polymer Battery," *Electrochimica Acta*, 46(4) pp. 599-605.
- [22] Shaju, K. M., and Bruce, P. G., 2008, *Chem. Mater.*, 20(17) pp. 5562.
- [23] U.S. Advanced Battery Consortium, 2006, "EV Battery Test Procedures Manual: Appendix G - USABC Criteria for Advanced Battery Technologies," .
- [24] Pasquier, A. D., Plitz, I., Gural, J., 2004, "Power-Ion Battery: Bridging the Gap between Li-Ion and Supercapacitor Chemistries," *Journal of Power Sources*, 136(1) pp. 160-170.
- [25] Lu, W., Lee, C. W., Venkatachalapathy, R., 2000, "Electrochemical and Thermal Behaviour of LiNi_{0.8}Co_{0.2}O₂ Cathode in Sealed 18650 Li-Ion Cells," *Journal of Applied Electrochemistry*, 30(10) pp. 1119-1124.
- [26] Chen, Y. H., Tang, Z. Y., Lu, X. H., 2006, "Research of Explosion Mechanism of Lithium-Ion Battery," *Progress in Chemistry*, 18(6) pp. 823-831.
- [27] Xia, Y., Fujieda, T., Tatsumi, K., 2001, "Thermal and Electrochemical Stability of Cathode Materials in Solid Polymer Electrolyte," *Journal of Power Sources*, 92(1-2) pp. 234-243.
- [28] Chang, H., Wu, H., and Wu, N., 2008, "Enhanced High-Temperature Cycle Performance of LiFePO₄/carbon Batteries by an Ion-Sieving Metal Coating on Negative Electrode," *Electrochemistry Communications*, 10(12) pp. 1823-1826.
- [29] Shim, J., and Striebel, K. A., 2003, "Cycling Performance of Low-Cost Lithium Ion Batteries with Natural Graphite and LiFePO₄," *Journal of Power Sources*, 119pp. 955-958.
- [30] DiLeo, R. A., Castiglia, A., Ganter, M. J., 2010, "Enhanced Capacity and Rate Capability of Carbon Nanotube Based Anodes with Titanium Contacts for Lithium Ion Batteries," *ACS Nano*, 4(10) pp. 6121-6131.
- [31] Vetter, J., 2005, "Ageing Mechanisms in Lithium-Ion Batteries," *Journal of Power Sources*, 147(1-2) pp. 269.
- [32] Belov, D., and Yang, M., 2008, "Failure Mechanism of Li-Ion Battery at Overcharge Conditions," *Journal of Solid State Electrochemistry*, 12(7-8) pp. 885-894.
- [33] Broussely, M., Biensan, P., Bonhomme, F., 2005, "Main Aging Mechanisms in Li Ion Batteries," *Journal of Power Sources*, 146(1-2) pp. 90-96.
- [34] Chen, G., and Richardson, T., 2009, "Solid Solution Phases in the Olivine-Type LiMnPO₄/MnPO₄ System," *Journal of the Electrochemical Society*, 156(9) pp. A756.
- [35] Sun, Y. C., Wang, Z. X., Chen, L. Q., 2003, "Improved Electrochemical Performances of Surface-Modified Spinel LiMn₂O₄ for Long Cycle Life Lithium-Ion Batteries," *Journal of the Electrochemical Society*, 150(10) pp. A1294-A1298.
- [36] Song, G., Wu, Y., Xu, Q., 2010, "Enhanced Electrochemical Properties of LiFePO₄ Cathode for Li-Ion Batteries with Amorphous NiP Coating," *Journal of Power Sources*, 195(12)

- pp. 3913-3917.
- [37] Shenouda, A. Y., and Liu, H. K., 2009, "Studies on Electrochemical Behaviour of Zinc-Doped LiFePO₄ for Lithium Battery Positive Electrode," *Journal of Alloys and Compounds*, 477(1-2) pp. 498-503.
- [38] Meethong, N., Huang, H. Y. S., Carter, W. C., 2007, "Size-Dependent Lithium Miscibility Gap in Nanoscale Li_{1-x}FePO₄," *Electrochemical and Solid State Letters*, 10(5) pp. A134-A138.
- [39] Chen, G., and Richardson, T., 2010, "Thermal Instability of Olivine-Type LiMnPO₄ Cathodes," *Journal of Power Sources*, 195(4) pp. 1221.
- [40] Cuisinier, M., Martin, J., Dupré, N., 2010, "Moisture Driven Aging Mechanism of LiFePO₄ Subjected to Air Exposure," *Electrochemistry Communications*, 12(2) pp. 238-241.
- [41] Tanguy, F., Gaubicher, J., Gaillot, A., 2009, "Lowering Interfacial Chemical Reactivity of Oxide Materials for Lithium Batteries. A Molecular Grafting Approach," *Journal of Materials Chemistry*, 19(27) pp. 4771-4777.
- [42] Vidu, R., and Stroeve, P., 2004, "Improvement of the Thermal Stability of Li-Ion Batteries by Polymer Coating of LiMn₂O₄," *Industrial & Engineering Chemistry Research*, 43(13) pp. 3314-3324.
- [43] Kang, B., and Ceder, G., 2009, "Battery Materials for Ultrafast Charging and Discharging," *Nature*, 458(7235) pp. 190-193.
- [44] Cuisinier, M., Martin, J., Dupré, N., 2010, "Moisture Driven Aging Mechanism of LiFePO₄ Subjected to Air Exposure," *Electrochemistry Communications*, 12(2) pp. 238-241.
- [45] Yamada, A., Koizumi, H., Nishimura, S., 2006, "Room-Temperature Miscibility Gap in Li_xFePO₄," 5(5) pp. 360.
- [46] Duong, T., 2010, "Directions for Energy Storage R&D in the Vehicle Technologies Program," *Symposium on Energy Storage Beyond Lithium Ion: Materials Perspectives*, Anonymous .
- [47] Chen, Y., Hu, C., and Li, Y., 2010, "Effects of Cathode Impedance on the Performances of Power-Oriented Lithium Ion Batteries," *Journal of Applied Electrochemistry*, 40(2) pp. 277-284.
- [48] Du Pasquier, A., Huang, C. C., and Spitler, T., 2009, "Nano Li₄Ti₅O₁₂-LiMn₂O₄ Batteries with High Power Capability and Improved Cycle-Life," *Journal of Power Sources*, 186(2) pp. 508-514.
- [49] Aurbach, D., Markovsky, B., Salitra, G., 2007, "Review on Electrode-Electrolyte Solution Interactions, Related to Cathode Materials for Li-Ion Batteries," *Journal of Power Sources*, 165(2) pp. 491-499.
- [50] Fu, L. J., Liu, H., Li, C., 2006, "Surface Modifications of Electrode Materials for Lithium Ion Batteries," *Solid State Sciences*, 8(2) pp. 113-128.
- [51] Sun, Y. K., Hong, K. J., Prakash, J., 2002, "Electrochemical Performance of Nano-Sized ZnO-Coated LiNi_{0.5}Mn_{1.5}O₄ Spinel as 5 V Materials at Elevated Temperatures," *Electrochemistry Communications*, 4(4) pp. 344-348.
- [52] Yamada, A., Koizumi, H., Sonoyama, N., 2005, "Phase Change in Li_xFePO₄," *Electrochemical and Solid State Letters*, 8(8) pp. A409-A413.
- [53] Liu, Z., and Huang, X., 2010, "Factors that Affect Activation Energy for Li Diffusion in LiFePO₄: A First-Principles Investigation," *Solid State Ionics*, 181(19-20) pp. 907-913.
- [54] Jahn, H. A., and Teller, E., 1937, "Stability of Polyatomic Molecules in Degenerate Electronic States. I. Orbital Degeneracy," *Proceedings of the Royal Society of London. Series A - Mathematical and Physical Sciences*, 161(905) pp. 220-235.
- [55] Tanguy, F., Gaubicher, J., Gaillot, A., 2009, "Lowering Interfacial Chemical Reactivity of Oxide Materials for Lithium Batteries. A Molecular Grafting Approach," *Journal of Materials Chemistry*, 19(27) pp. 4771-4777.
- [56] Doi, T., Kageura, J., Okada, S., 2008, "Surface Modification of LiNi_{1/2}Mn_{3/2}O₄ Thin-Films by Zirconium alkoxide/PMMA Composites and their Effects on Electrochemical Properties," *Journal of Power Sources*, 185(1) pp. 473-479.
- [57] Changjiu, L., Huijing, W., Huabin, W., 2007, "Study on Physical Speciality and Electrochemical Characteristics of Electrode Material of Amorphous Nano-Ni(OH)₂," *Rare Metal Materials and Engineering*, 36(9) pp. 1545-1548.
- [58] Xia, Y., Kumada, N., and Yoshio, M., 2000, "Enhancing the Elevated Temperature Performance of Li/LiMn₂O₄ Cells by Reducing LiMn₂O₄ Surface Area," *Journal of Power Sources*, 90(2) pp. 135-138.
- [59] Lanz, M., Kormann, C., and Novak, P., 2003, "A Procedure for Specific Charge and Cycling Performance Measurements on LiMn₂O₄ Spinel for Lithium-Ion Batteries," *Journal of Solid State Electrochemistry*, 7(9) pp. 658-664.
- [60] Broussely, A., Blanchard, P., Biensan, P., 2003, "Properties of Large Li Ion Cells using a Nickel Based Mixed Oxide," *Journal of Power Sources*, 119 pp. 859-864.
- [61] Albrecht, S., Kumpers, J., Kruff, M., 2003, "Electrochemical and Thermal Behavior of Aluminum- and Magnesium-Doped Spherical Lithium Nickel Cobalt Mixed Oxides Li_{1-x}(Ni_{1-y-z}Co_yM_z)O₂ (M = Al, mg)," *Journal of Power Sources*, 119, pp. 178-183.
- [62] Chen, G., Song, X., and Richardson, T. J., 2006, "Electron Microscopy Study of the LiFePO₄ to FePO₄ Phase Transition," *Electrochemical and Solid-State Letters*, 9(6) pp. A295-A298.
- [63] Bhandakkar, T. K., and Gao, H., 2010, "Cohesive Modeling of Crack Nucleation Under Diffusion Induced Stresses in a Thin Strip: Implications on the Critical Size for Flaw Tolerant Battery Electrodes," *International Journal of Solids and Structures*, 47(10) pp. 1424-1434.
- [64] Cheng, Y. V., Mark W., 2010, "Diffusion-Induced Stress, Interfacial Charge Transfer, and Criteria for Avoiding Crack Initiation of Electrode Particles " *Journal of the Electrochemical Society*, 157(4) pp. A508-A516.
- [65] Meethong, N., Huang, H. Y. S., Speakman, S. A., 2007, "Strain Accommodation during Phase Transformations in Olivine-Based Cathodes as a Materials Selection Criterion for High-Power Rechargeable Batteries," *Advanced Functional Materials*, 17(7) pp. 1115-1123.
- [66] Eshelby, J. D., Read, W. T., and Shockley, W., 1953, "Anisotropic Elasticity with Applications to Dislocation Theory," *Acta Metallurgica*, 1(3) pp. 251-259.
- [67] Heinisch, H. J., G. Sines, J. Goodman, 1975, "Elastic Stresses and Self-Energies of Dislocations of Arbitrary Orientation in Anisotropic Media: Olivine, Orthopyroxene, Calcite, and Quartz," *J. Geophys. Res.*, 80(14) pp. 1885-1896.
- [68] Ohsawa, K., 2009, "Stress Function for Dislocation Loops in Anisotropic Crystals," *IOP Conference Series: Materials Science and Engineering*, 3(1) pp. 012027.
- [69] Gabrisch, H., Wilcox, J., and Doeff, M. M., 2008, "TEM Study of Fracturing in Spherical and Plate-Like LiFePO₄ Particles," *Electrochemical and Solid State Letters*, 11(3) pp. A25-A29.
- [70] Hull, D., and Bacon, D.J., 2001, "Introduction to dislocations," *Butterworth-Heinemann, Oxford Oxfordshire* ;

- Boston, pp. 242.
- [71] Indenbom, L., 1992, "Elastic strain fields and dislocation mobility," Amsterdam; New York: Elsevier Science Publishers; New York, NY, USA: Sole distributor for the USA and Canada, Elsevier Science Pub., 1992.
- [72] Maxisch, T., and Ceder, G., 2006, "Elastic Properties of Olivine LiFePO_4 from First Principles," *Physical Review B*, 73(17) pp. 174112.
- [73] Huang, HYS and Wany, YX, 2012, "Dislocation Based Stress Developments in Lithium-ion Batteries," *Journal of The Electrochemical Society*, 159(6) pp. A815-A821.

Available online at:

<http://tsest.org/index.php/TCMS/article/view/61>

Download full text article at:

<http://tsest.org/index.php/TCMS/article/download/61/36>

Cite this work as:

Yixu Richard Wang and Hsiao-Ying Shadow Huang, "Lithium-Ion Battery Materials and Mechanical Stress Fields" *TSEST Transaction on Control and Mechanical Systems*, Vol. 1, No. 5, PP. 192-200, Sep., 2012.